

Origin of critical-temperature enhancement of an iron-based high- T_c superconductor, $\text{LaFeAsO}_{1-x}\text{F}_x$: NMR study under high pressure

Tatsuya Nakano¹, Naoki Fujiwara^{1*}, Kenichiro Tatsumi¹, Hironari Okada^{2,3}, Hiroki Takahashi^{2,3}, Yoichi Kamihara^{3,4}, Masahiro Hirano^{5,6}, and Hideo Hosono^{4,5,6}

¹ Graduate School of Human and Environmental Studies, Kyoto University,

Yoshida-Nihonmatsu-cyo, Sakyo-ku, Kyoto 606-8501, Japan*

² Department of Physics, College of Humanities and Sciences,

Nihon University, Sakurajosui, Setagaya-ku, Tokyo 156-8550

³ TRiP, Japan Science and Technology Agency (JST),

Sanban-cho bldg. 5, Sanban-cho, Chiyoda-ku, Tokyo 102-0075, Japan

⁴ Materials and Structures Laboratory (MSL), Tokyo Institute of Technology,

4259 Nagatsuda, Midori-ku, Yokohama 226-8503, Japan

⁵ ERATO-SORST, Japan Science and Technology Agency (JST),

Sanban-cho bldg. 5, Sanban-cho, Chiyoda-ku, Tokyo 102-0075, Japan and

⁶ Frontier Research Center (FRC), Tokyo Institute of Technology,

4259 Nagatsuda, Midori-ku, Yokohama 226-8503, Japan

(Dated: September 1 2009)

Nuclear magnetic resonance (NMR) measurements of an iron (Fe)-based superconductor $\text{LaFeAsO}_{1-x}\text{F}_x$ ($x = 0.08$ and 0.14) were performed at ambient pressure and under pressure. The relaxation rate $1/T_1$ for the overdoped samples ($x = 0.14$) shows T -linear behavior just above T_c , and pressure application enhances $1/T_1T$ similar to the behavior of T_c . This implies that $1/T_1T = \text{constant}$ originates from the Korringa relation, and an increase in the density of states at the Fermi energy $D(E_F)$ leads to the enhancement of T_c . In the underdoped samples ($x = 0.08$), $1/T_1T$ measured at ambient pressure also shows T -independent behavior in a wide temperature range above T_c . However, it shows Curie-Weiss-like T dependence at 3.0 GPa accompanied by a small increase in T_c , suggesting that predominant low-frequency antiferromagnetic fluctuation is not important for development of superconductivity or remarkable enhancement of T_c . The qualitatively different features between underdoped and overdoped samples are systematically explained by a band calculation with hole and electron pockets.

PACS numbers: 74.70. -b, 74.25. Ha, 74.62. Fj, 76.60. -k

$\text{LaFeAsO}_{1-x}\text{F}_x$ is the highly important compound that stimulated tremendous research activity in Fe-based high- T_c superconductors¹⁾. The compound exhibits several phases with F substitution, i.e., electron doping, on the temperature-concentration ($T - x$) phase diagram^{1,2)}. A spin-density-wave (SDW)-type antiferromagnetic (AF) ordering of the parent compound LaFeAsO is suppressed by F substitution, and superconductivity appears after the AF phase vanishes³⁻⁵⁾. T_c weakly depends on the doping level. The optimal doping level is around $x = 0.11$, at which T_c reaches 26 K. Similar phenomena also appear in a "122" system, $(\text{K}_{1-x}\text{X}_x)\text{Fe}_2\text{As}_2$ ($\text{X}=\text{Sr}$ or Ba)⁶⁻⁹⁾.

The $T - x$ phase diagram is reminiscent of hole doping in high- T_c cuprates. However, unlike the case of high- T_c cuprates, it is unclear whether AF spin fluctuation plays an important role in raising T_c . In the case of $\text{LaFeAsO}_{1-x}\text{F}_x$, T_c is sensitive to pressure (P), and shows a clear dome-shaped pressure dependence on the $T - P$ phase diagram¹⁰⁾. The highest T_c is realized by applying pressure to optimally doped samples ($x \sim 0.11$) or heavily doped samples ($x \sim 0.14$): T_c of 26 and 20 K

for $x = 0.11$ and 0.14 , respectively, goes up to 43 K with application of a pressure of 4-5 GPa¹⁰⁻¹²⁾. (Fig. 1(a).) However, T_c for lightly doped samples ($x = 0.05$) hardly goes beyond 30 K even under high pressure^{11,12)}. The suppression of T_c suggests that a superconducting state with a high T_c is realized apart from the antiferromagnetically ordered phase on the $T - x$ phase diagram. To investigate the origin of the T_c enhancement under pressure, and the relationship between the low-frequency AF spin fluctuation and superconductivity in this material, we performed ^{75}As ($I = 3/2$)-nuclear magnetic resonance (NMR) measurements under high pressure of underdoped samples ($x = 0.08$) and overdoped samples ($x = 0.14$). To determine T_c and investigate the P dependence, we also measured resistivity at pressures below 2.6 GPa using a piston-cylinder-type pressure cell, and resistance above 4 GPa using a diamond anvil cell.

The resistance and resistivity for $x = 0.08$ are plotted in Figs. 1(b) and (c), respectively. The resistivity for $x = 0.14$ has been published elsewhere^{11,12)}. Their T_c values are determined by the onset of superconductivity. In both samples, zero resistivity was confirmed at low temperatures. The P dependence of T_c for $x = 0.08, 0.11$, and 0.14 is plotted in Fig. 1(a). T_c for the underdoped regime ($x < 0.11$) does not go beyond 35 K, whereas that for the overdoped regime ($x > 0.11$) exceeds 40 K.

*Electronic address: naoki@fujiwara.h.kyoto-u.ac.jp

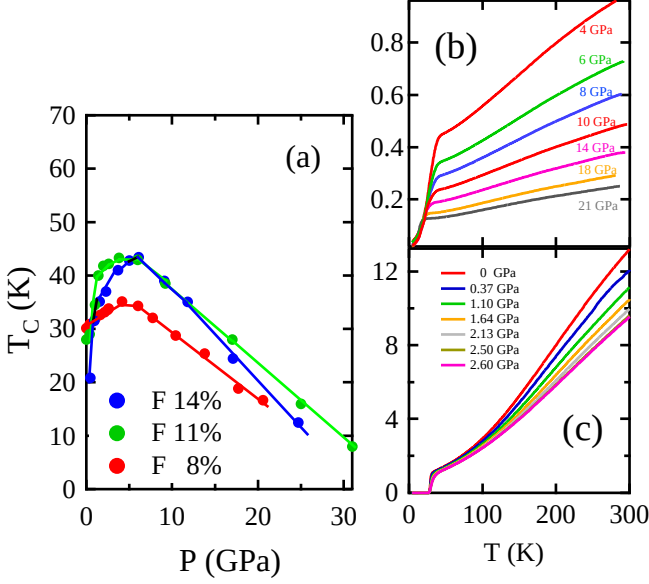


FIG. 1: (a) P dependence of T_c measured using a piston-cylinder cell and a diamond anvil cell. (b) Resistance for 8% doped samples at various pressures measured using a diamond anvil cell. The unit of the vertical axis is Ω . (c) Resistivity for 8% doped samples at various pressures measured by using a piston-cylinder cell. The unit of the vertical axis is Ωcm .

We measured NMR spectra under pressure using randomly oriented powder samples. Field ($\mathbf{H}$)-swept spectra of the central transition, $I = -1/2 \rightleftharpoons 1/2$, show a broad powder pattern, which prevented accurate Knight shift measurements (Fig. 2 inset). The line shape is explained by considering the second order quadrupole effect under a magnetic field¹³. The resonance position depends on the angle θ between $\mathbf{H}$ and the maximum electric field gradient (EFG) at an As nucleus¹³. The lower- and higher-field peaks in the inset correspond to $\theta = 90$ and 42° , respectively. The separation between them is proportional to the square of the pure quadrupole frequency (ν_Q) except for a minor correction due to the asymmetry parameter (η) of the EFG tensor¹⁴. We estimated η as 0.1 from the NMR spectra and found that η is insensitive to the doping level. The frequency ν_Q is defined as $2\nu_Q = eQV_{zz}/h$, where Q and V_{zz} are the nuclear quadrupole moment and maximum EFG, respectively. The separation between the peaks decreases with increasing pressure. The results of ν_Q at several pressures are plotted in the main panel of Fig. 2. The frequency ν_Q , i.e., V_{zz} originates from the on-site charge density and the surrounding Fe ions. V_{zz} is sensitive to the distance between Fe and As ions: a stretching of the Fe-As distance decreases EFG originating from the surrounding Fe ions and weakens the hybridization between As-4p and Fe-3d orbitals, which would lead to the decrease in the on-site charge density. The decrease in ν_Q or EFG due to application of pressure can be explained by the stretching

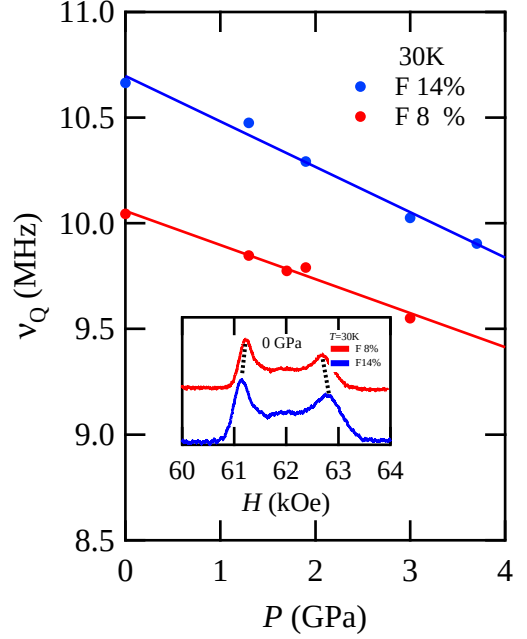


FIG. 2: P dependence of pure quadrupole frequency of ^{75}As nuclei. The inset shows field-swept spectra of the central transition, $I = -1/2 \rightleftharpoons 1/2$.

of the Fe-As distance. The stretching due to application of pressure has been observed from synchrotron radiation measurements under high pressure¹⁵.

We measured the relaxation rate $1/T_1$ at $\theta = 90^\circ$ using a saturation recovery method. The T dependence of $1/T_1$ for $x = 0.08$ and 0.14 is shown in Figs. 3(a) and (b), respectively. The T dependence of $1/T_1 T$ is shown in Fig. 4. $1/T_1$ for the two doping levels shows qualitatively different T dependence.

In the case of $x = 0.14$, T -linear dependence is observed in a narrow T range just above T_c . The T -linear dependence is clearly observed as a plateau in Fig. 4. T_c values determined from the resistivity measurements are indicated by arrows in Figs. 3 (b) and 4. The value of $1/T_1 T$ is enhanced with increasing pressure similar to the behavior of T_c . $1/T_1 T$ seems to change in accordance with T_c with increasing pressure: both $1/T_1 T$ and T_c increase remarkably with increasing pressure from 0 to 3.0 GPa, and the change in $1/T_1 T$ between 3.0 and 3.7 GPa is small, similar to that in T_c . The T -linear dependence is attributable to the Korringa relation, and the value of $1/T_1 T$ just above T_c is proportional to the square of the density of states (DOS) at the Fermi energy, $D(E_F)$. At high temperatures, deviation from the T -linear dependence becomes remarkable. The increase in $1/T_1 T$ can be explained by a characteristic band structure of this system, as described below¹⁶. At low temperatures, another T -linear dependence appears, suggesting the existence of the impurity scatterings^{17–19}. In the

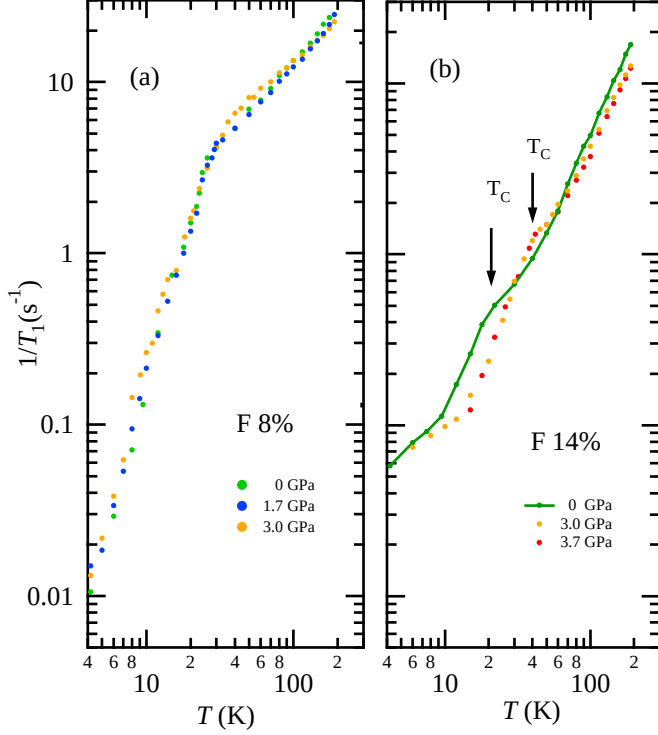


FIG. 3: ^{75}As -nuclear magnetic relaxation rate $1/T_1$ for $\mathbf{H} \perp$ the maximum electric field gradient of ^{75}As . (a) Underdoped regime ($x = 0.08$). (b) Overdoped regime ($x = 0.14$).

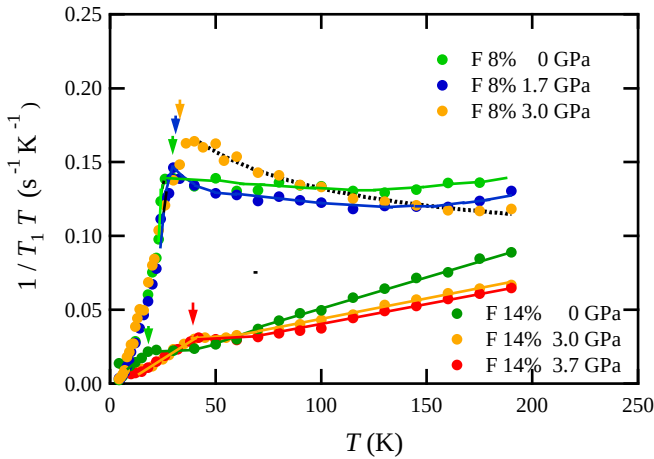


FIG. 4: $1/T_1T$ measured at several pressures. The dotted curve represents a Curie-Weiss curve. The other lines are guides to the eye.

overdoped regime, the system can be well described as a band metal, and application of pressure causes an increase in $D(E_F)$ and enhancement of T_c .

In the case of $x = 0.08$, $1/T_1$ shows T -linear dependence in a wide T range above T_c at ambient pressure, and T^3 dependence below T_c , as already reported by

other groups^{20–22}. T_c values determined from the resistivity measurements, indicated by arrows in Fig. 4, are consistent with those estimated from the change in $1/T_1T$ within an accuracy of several Kelvins. At first glance, the T -linear dependence is reminiscent of the Korringa relation, as in the case of $x = 0.14$. However, it does not originate from the conventional Korringa relation: if the T -linear dependence originates from the Korringa relation, the estimated T_c should go beyond 40 K because the value of $1/T_1T$, namely, $D(E_F)$ for $x = 0.08$ is much larger than that for $x = 0.14$. Furthermore, $1/T_1T \sim \text{constant}$, observed at ambient pressure, breaks down under high pressure, as seen from the data at 3.0 GPa. $1/T_1T$ increases monotonously toward T_c . $1/T_1T$ at 1.7 GPa shows transitional behavior from $1/T_1T \sim \text{constant}$ to Curie-Weiss behavior. The dotted curve in Fig. 4 represents a Curie-Weiss curve: $1/T_1T = 0.09 + 6.2/(T + 39)$ ($s^{-1}K^{-1}$). The Curie-Weiss behavior is reminiscent of high- T_c cuprates. Although low-frequency AF fluctuation predominates by applying pressure, an increase in T_c is small. Low-frequency AF fluctuation is not essential to achieving the highest T_c , although it would contribute to raising T_c to some extent: the highest T_c is realized for $x = 0.11$ -0.14 without development of low-frequency AF fluctuation. It is concluded that low-frequency AF fluctuation suppresses the development of superconductivity or the enhancement of T_c in this material.

The qualitatively different features between samples with $x = 0.08$ and 0.14 are explained by a scenario based on a band calculation with electron and hole pockets^{23,24}. The system can be treated as a simple two-dimensional square lattice of an Fe atom, although two Fe atoms are contained in the actual unit cell. In the unfolded Brillouin zone (Bz), hole pockets exist around $\Gamma(0,0)$ and $\Gamma'(\pi,\pi)$ in addition to electron pockets around M points²³. $\Gamma'(\pi,\pi)$ overlaps $\Gamma(0,0)$ in the original folded Brillouin zone. With increasing doping level, the Fermi energy moves upward, and the hole pockets around $\Gamma(\Gamma')$ become smaller. The hole pocket around $\Gamma'(\pi,\pi)$ is sensitive to the doping level, and it first vanishes with increasing doping level, as illustrated in Fig. 5²⁵. In the underdoped regime, the nesting between electron and hole pockets gives rise to AF fluctuation, which predominates and would suppress development of superconductivity, namely remarkable enhancement of T_c . Application of pressure seems to promote the nesting. In the overdoped regime, the nesting becomes weak when electron doping moves the Fermi energy upward and the hole pockets around $\Gamma(\Gamma')$ become smaller. In such a situation, remarkable enhancement of T_c is possible. When the hole pocket around Γ' vanishes, a large weight of DOS still remains just below the Fermi energy as illustrated in Fig. 5. The contribution from these energy levels presumably leads to an increase in $1/T_1T$ at high temperatures, as seen in the $x = 0.14$ doped samples. The scenario can be expanded to other systems, such as hole-doped systems: in this case the Fermi energy moves downward with increasing doping

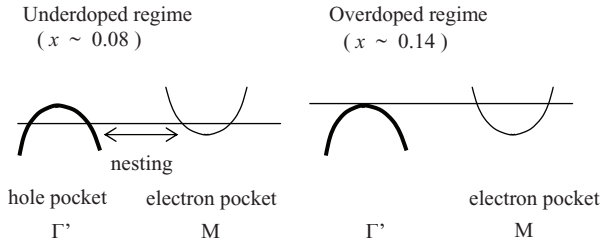


FIG. 5: A scheme of a two-band model. In the underdoped regime, nesting between hole and electron pockets causes antiferromagnetic fluctuation as seen in $1/T_1T$ for the 8% doped samples at 3.0 GPa (Fig. 4). In the overdoped regime, the hole pockets around Γ' disappears, and the system can be described as a band metal. The behavior is seen in $1/T_1T$ for the 14% doped samples (Fig. 4).

level, and AF fluctuation predominates until the Fermi energy comes across the bottom of the electron band, which would suppress any rise in T_c . This scenario may answer the question of why the highest T_c (over 50 K) is realized only for "1111" systems. To investigate the origin of the highest T_c observed in a "1111" system, the pressure effect on the electron pockets around M seems important.

We would like to thank K. Kuroki, and H. Ikeda for fruitful discussions and A. Hisada for experimental support. This work was partially supported by a Grant-in-Aid (KAKENHI 17340107) from the Ministry of Education, Science and Culture, Japan.

- ¹ Y. Kamihara, T. Watanabe, M. Hirano, and H. Hosono, J. Am. Chem. Soc. **130**, 3296 (2008).
- ² H. Luetkens, H.-H. Klauss, M. Kraken, F. J. Litterst, T. Dellmann, R. Klingeler, C. Hess, R. Khasanov, A. Amato, C. Baines, M. Kosmala, O. J. Schumann, M. Braden, J. Hamann-Borrero, N. Leps, A. Kondrat, G. Behr, J. Werner, and B. Büchner, Nature Materials, **8**, 305 (2009).
- ³ C. de la Cruz, Q. Huang, J. W. Lynn, J. Li, W. Ratcliff II, J. L. Zarestky, H. A. Mook, G. F. Chen, J. L. Luo, N. L. Wang, and P. Dai Nature **453**, 899 (2008).
- ⁴ H.-H. Klauss, H. Luetkens, R. Klingeler, C. Hess, F. J. Litterst, M. Kraken, M. M. Korshunov, I. Eremin, S.-L. Drechsler, R. Khasanov, A. Amato, J. Hamann-Borrero, N. Leps, A. Kondrat, G. Behr, J. Werner, and B. Buchner, Phys. Rev. Lett. **101**, 077005 (2008).
- ⁵ Q. Huang, J. Zhao, J. W. Lynn, G. F. Chen, J. L. Luo, N. L. Wang, and P. Dai, Phys. Rev. B **78**, 054529 (2008).
- ⁶ K. Sasmal, L. Bing, B. Lorenz, A. M. Guloy, F. Chen, Y. Y. Xue, and C. W. Chu, Phys. Rev. Lett. **101**, 107007 (2008).
- ⁷ M. Rotter, M. Tegel, and D. Johrendt, Phys. Rev. Lett. **101**, 107006 (2008).
- ⁸ H. Chen, Y. Ren, Y. Qiu, Wei Bao, R. H. Liu, G. Wu, T. Wu, Y. L. Xie, X. F. Wang, Q. Huang, and X. H. Chen, Europhys. Lett. **85**, 17006 (2009).
- ⁹ K. Igawa, H. Okada, H. Takahashi, S. Matsuishi, Y. Kamihara, M. Hirano, H. Hosono, K. Matsubayashi, and Y. Uwatoko, J. Phys. Soc. Jpn. **78**, 025001 (2009).
- ¹⁰ H. Takahashi, K. Igawa, K. Arii, Y. Kamihara, M. Hirano, and H. Hosono, Nature **453**, 376 (2008).
- ¹¹ H. Okada, K. Igawa, H. Takahashi, Y. Kamihara, M. Hirano, H. Hosono, K. Matsubayashi, and Y. Uwatoko, J. Phys. Soc. Jpn. **77**, 113712 (2008).
- ¹² H. Takahashi, H. Okada, K. Igawa, K. Arii, Y. Kamihara, S. Matsuishi, M. Hirano, H. Hosono, K. Matsubayashi, and Y. Uwatoko, J. Phys. Soc. Jpn. Suppl. C **77**, 78 (2008).
- ¹³ G. H. Stauss, J. Chem. Phys. **40**, 1988 (1964).
- ¹⁴ The asymmetry parameter η is defined as $\eta = \frac{V_{xx} - V_{yy}}{V_{zz}}$, where V_{zz} , V_{xx} and V_{yy} ($V_{xx} \leq V_{yy}$) represent the maximum EFG and EFGs for the axes orthogonal to the principal axis z , respectively.
- ¹⁵ G. Garbarino, P. Toulemonde, M. Alvarez-Murga, A. Sow, M. Mezouar and M. Nunez-Regueiro, Phys. Rev. B **78**, 100507 (2008).
- ¹⁶ H. Ikeda, J. Phys. Soc. Jpn. **77**, 123707 (2008).
- ¹⁷ K. Tatsumi, N. Fujiwara, H. Okada, H. Takahashi, Y. Kamihara, M. Hirano, H. Hosono, J. Phys. Soc. Jpn. **78**, 023709 (2009).
- ¹⁸ D. Parker, O. V. Dolgov, M. M. Korshunov, A. A. Golubov, and I. I. Mazin, Phys. Rev. B **78**, 134524 (2008).
- ¹⁹ Y. Bang, H.-Y. Choi, H. Won, Phys. Rev. B **79**, 054529 (2009).
- ²⁰ Y. Nakai, K. Ishida, Y. Kamihara, M. Hirano, H. Hosono, J. Phys. Soc. Jpn. **77**, 07370 (2008).
- ²¹ H. J. Grafe, D. Paar, G. Lang, N. J. Curro, G. Behr, J. Werner, J. Hamann-Borrero, C. Hess, N. Leps, R. Klingeler, and B. Büchner, Phys. Rev. Lett. **101**, 047003 (2008).
- ²² S. Kawasaki, K. Shimada, G. F. Chen, J. L. Luo, N. L. Wang, and Guo-qing Zheng, **78**, 220506 (2008).
- ²³ K. Kuroki, S. Onari, R. Arira, H. Usui, Y. Tanaka, H. Kontani, and H. Aoki, Phys. Rev. Lett. **101**, 087004 (2008).
- ²⁴ I. I. Mazin, D. J. Singh, M. D. Johannes, and M. H. Du, Phys. Rev. Lett. **101**, 057003 (2008).
- ²⁵ The hole pocket around Γ' vanishes at $x = 0.1$ (see Ref. [23]) although both of hole pockets around Γ and Γ' exist for the undoped samples ($x = 0$) (see Ref. [16]).